



Production of Aluminum Matrix Composite Material by Active Carbon Additive

Ayman M. S. Eisay¹ · Aydın Turkyilmaz²

Received: 11 March 2021 / Accepted: 4 June 2021 / Published online: 9 June 2021

© The Author(s), under exclusive licence to Springer Science+Business Media, LLC, part of Springer Nature 2021

Abstract

The effectiveness of composite materials with the addition of activated carbon produced from biomaterial with a new application on aluminum-based composite materials was investigated in this study. Activated carbon was produced from the peanut shells via the chemical activation method and the obtained activated carbon was mixed with aluminum and composite material. For the characterization of the composite material obtained, XRD and SEM–EDS optical photographs were assessed in the experimental process. According to Vickers Hardness and Dynamic Micro Hardness results, the sample with the hardness value of 2% AC added had the highest hardness value. The value of the elastic modulus was found to be 9.59GPa with an increase of 3.4 times compared to aluminum with 2% activated carbon addition. This increases with activated carbon quantity, and weakens the composite structure due to weak van der Waals interaction with aluminum, which reduces hardness; therefore, the best ratio of the activated carbon reinforcement to the aluminum matrix was obtained at 2% activated carbon addition.

Keywords Composite materials · Aluminum · Activated carbon · Characterization · Peanut shell

1 Introduction

Aluminum and aluminum composites are used very frequently in areas such as automotive, aerospace industry due to their properties such as high thermal and electrical conductivity and good corrosion resistance [1]. The utilization of aluminum composites in aerospace industries has increased due to their lighter weight [2]. Increasing demands for light-weight materials for improving the efficiency of vehicles is the main driver behind the current research and development of aluminum composites [3]. Metals having a reduced specific gravity have useful mechanical characteristics including strength, which provides the required strength with less weight, and thereby reducing fuel and operating costs. They have high electric and thermal conductivity,

high damping capacity, and high corrosion resistance [4]. AMCs have created interest in research communities since 1920s [5]. One of the main reasons to conduct the current research was to find out which material is appropriate for composite preparation. Since it is a metal matrix composite, we had several options to fill up the slots of the matrix and several options for reinforcement materials. The next task was composite preparation. To prepare that, the reinforcement and method type have to be decided beforehand [2]. We focused on the materials which have contributed to the aircraft industry and in the developments in metal matrix composites; therefore, we chose aluminum as our matrix material. Various research is still ongoing on analyzing multi-faceted characteristics of aluminum. Besides the contributions of aluminum to our industry in the previous years also made a key point in selecting it, selecting the reinforcement was a different task, for which we had to know how to mix both the materials and type of reinforcement to be used [2, 6]. Carbon and its allotropes are widely used in composite materials. Especially graphene is widely used in nanoelectronic devices [7]. The use of graphene in such fields has made a significant contribution to the scientific field. [8]. Graphene-like materials are the most important structures due to their mechanical, thermal, electronic,

✉ Aydın Turkyilmaz
aturkyilmaz@kastamonu.edu.tr

¹ Ministry of Higher Education and Scientific Research,
University of Zawia Faculty of Engineering, Libya 54564,
Libya

² Faculty of Engineering and Architecture, Department
of Environmental Engineering, Kastamonu University,
Kastamonu 37150, Turkey

optical and thermoelectric properties. [9]. Bafekry et al., in their study with garefen hetero multilayer platinum mineral jacutingaite, investigated the optical, thermoelectric and mechanical properties and showed that the increase in the number of layers in PHS has a positive effect on the UV increase [10]. Thus, composite materials, particularly metal matrix composites, have taken aluminum's place due to the enhancement of mechanical properties of aluminum alloys via reinforcements. Thus, composite materials' major benefits include their strength, which is very useful to improve the structural performance of spacecraft and military equipment. Mechanical characteristics and the wear resistance of Al 7075 graphite composites were studied during research [11], into carbon-reinforced aluminum composites [12] and characteristics and microstructures of Al_2O_3 , SiC, and B_4C , reinforced Al [13]. Activated Nano-composites of carbon were used with alumina. It was synthesized and applied to remove sulphide ions from water [14]. Wear behavior and physical properties of aluminum have been discussed along with palm shell activated carbon [15]. We utilized reinforcement in particulate form, which suits the composite preparation technique, and reinforcement was nothing other than activated carbon. Activated carbon was produced via a slight modification to carbon, after which, carbon remains in a stable form [13]. For economic reasons, and as it is a renewable source, agricultural by-products and waste materials have been explored for activated carbon production for a long time [16]. Activated carbon has some excellent properties, which exist in active form: it can be highly porous, shows higher absorption rates, possesses the capacity to bind substances using London dispersion force or Van der Waals force, exhibits higher absorption rates, shows more reactivity than carbon, prevents corrosion and plays a significant role in gold, water, and gas purification processes, air filtration, and metal extraction [17]. Processing results in additional surface area for chemical reactions or absorption [18]. The reinforcement multi-walled carbon nanotubes are added in the various ratios between 2 and 10% weight of AA6061 alloy [19]. Bafekry et al. in which the electronic and optical properties of two-dimensional materials were examined, they showed that the band gap decreased by increasing the thickness of C2N. In his study [9]. According to our knowledge, aluminum composite materials with an aluminum matrix and with aluminum composite materials containing activated carbon are not available in the literature, although there are many studies in the literature where carbon nanotubes are used in this manner.

The present study aimed to obtain a new type of composite material by using aluminum matrix reinforcement of activated carbon obtained from the vegetable waste. Then, it was also aimed to obtain activated carbon as reinforcements with porous aluminum matrix composite material produced by powder metallurgical method. Moreover, it was also focused

on the mechanical properties by conducting hardness and density tests, as well as microstructure tests such as SEM, EDS, and XRD to improve the performance.

2 Materials and Experimental Setup

2.1 Preparation of Activated Carbon

Activation of activated carbons used in experiments was performed by mixing 5 M 250 ml HNO_3 and 50 g powdered peanut shells, after which it was left at room temperature for 1 day to remove structures outside the carbon skeleton of the peanut shells. Then, the samples were dried in the oven at 105 °C for 1 day and were pyrolyzed in a stainless-steel closed reactor vessel at 800 °C for 2 h under a constant N_2 nitrogen flow of 10 psi. The samples were then left to cool under a constant N_2 nitrogen flow. The cooled samples were removed from the reactor and subjected to washing with a 1 M NaOH solution for neutralization. Afterwards, the samples were washed 3–4 times with warm distilled water and dried in the oven at 110 °C for 1 day. The dried samples were grinded again in the grinder and sieved through the sieve to bring the particle size to 0–50 μm .

2.2 Preparation of Activated Carbon-aluminum Composite

Aluminum-based materials increases the mechanical strength of composite materials [20]

. Because of this in this study, activated carbon was added in varying proportions (2%, 4%, 6%) to powdered Aluminum with 99% purity and average particle size of 17–30 μm . and later, the composites were prepared by mixing aluminum with activated carbon by mechanical alloying. The mechanical alloying was conducted using a PM 100 Retsch planetary ball mill. The mill has a steel vial with a depth of 60 mm and a cylindrical cavity with a diameter of 100 mm. Nine small steel balls were selected, which each had a 12 mm diameter. They were selected to strengthen the metal bonds. 150 rpm was the rotational speed of milling. The vial contained 100 g of powdered mixture and steel balls, which was sealed in a pure argon atmosphere. The first batch of composite powders was Al and AC-based with the composition of: Al-2wt %AC, Al-4wt %AC, and Al-6wt %AC. The mixture was placed in a storage tube so as to lose contact with air and oxidization. Finally, the Al-Active carbon composite material was obtained using a metallographic sample preparation method. The powder mixture was loaded in a cylindrical mold with an inner diameter of 13 mm, and the powder was placed under 500 MPa. On a quartz tube, a circular disk was loaded in a MTI GSL-1100X-S50 furnace. When the protective argon gas was supplied to the specimen, the

temperature was increased to 550 °C. temperature increase was 10 °C per minute. This sintering temperature required almost 1 h waiting time. The specimen was later naturally cooled down. The resulting composite pellet keller solution (190 ml pure water + 5 ml HNO₃ + 3 ml HCl + 2 ml HF) was etched (Table 1).

3 Characterization of Activated Carbon and Composite Materials

The composition of the material was determined using the energy-dispersive X-ray spectroscopy (EDS) technique. The optical images of the samples were captured using an Olympus GX41 inverted metallurgical microscope. The scanning electron microscope (SEM) images were captured using the FEI Quanta 250 FEG-SEM. The stiffness of the composite is due to strengthening of particle reinforcements with a low aspect ratio. The ASTM E10 standard is used to test hardness. The Brinell test was adapted to find the metal hardness. A ball type indenter with 10 mm diameter is applied at 5 N load.

For determining sample hardness through hot pressing, the sample hardness was measured with the help of a Brinell hardness testing device at 62.5 kg load with a 2.5 mm ball diameter. For completeness in determining hardness, the measurement of hardness values was initiated from samples' middle, tip, center, and backside; thus, 3 values of hardness were measured for each sample. Later, the lowest and the highest values were eliminated, and the average hardness values were calculated taking into account the remaining values.

The aluminum matrix composites' densities were calculated with the help of a QUANTACHROME and ULTRAPYC Model 1200E helium pycnometer. The density was calculated and applied to the lower part of the bolstered samples and metals. We selected the Archimedes principle, which is a density measurement method. Archimedes' principle was applied to find the results, which are expressed through the following expressions for composites' densities.

Density of activated carbons:

$$\rho_{AC} = \frac{W_o}{V_p - \frac{W_t - (W_p + W_o)}{d_s}} \quad (1)$$

Volume of activated carbon:

$$V_{AC} = V_p - \frac{W_t - (W_p + W_o)}{d_s} \quad (2)$$

where;

Weight of pycnometer: W_p.

Weight of activated carbon: W_o.

(Pycnometer + Activated carbon + Liquid): W_t.

The density of pure liquid: d_s.

The volume of pycnometer: V_p.

The AC-Al composites' theoretical densities were calculated with the help of this rule of mixture:

$$\rho_t = \rho_{AL} \times \frac{W}{W}\% + \rho_{AC} \times \frac{W}{W}\% \quad (3)$$

$$\rho_b = \frac{\rho_{AC}}{\rho_t} \times 100 \quad (4)$$

Here;

ρ_{AC} = Experimentally calculated density (gr/cm³).

ρ_b = Relative density (%).

ρ_t = Theoretical density based on powder mixture rate (gr/cm³).

4 Results and Discussion



4.1 Microstructure and Composition

Figure 1(a–c) shows that it seems homogenous and well embedded in the Al matrix, and contains 2.0% mass of the AC sample. As with the samples produced by powder metallurgy, pore formation occurred in them. Active carbon beads are not embedded in aluminum, but aluminum beads are placed at the contact points. It has also been observed that the practical size of the activated carbon atoms is not equal. According to the SEM images of the samples used in the production of active carbon, additional composite materials were obtained from vegetables when aluminum is used as matrix; so, it is obvious in the SEM and mapping images and SEM photographs show that 2%, 4% and 6% activated carbon by weight was added to the aluminum matrix and so, activated carbon were homogeneously distributed in the matrix. No agglomeration was observed. In addition, activated carbon has homogeneous distribution in the samples, which increases the strength obtained composite material. When Fig. 2 is examined, comparing the optical image of a pure aluminum sample with the

Table 1 Activated carbons bet surface area and other properties

Samples	Bet surface area (m ² /g)	Weight % C	Weight % O	Weight % Al
Raw Peanut shell	0.83	29.9	22.5	0
Activated Carbon	82.9	55.07	10.67	0
Al + %2 AC		2	0	98.00
Al + %4 AC		4	0	96.00
Al + %6 AC		6	0	94.00

Fig. 1 SEM image and Energy dispersive spectrometer measurement (EDS) from these phases are given of Al–AC composites: (a) 2% AC, (b) 4% AC, (c) 6% AC

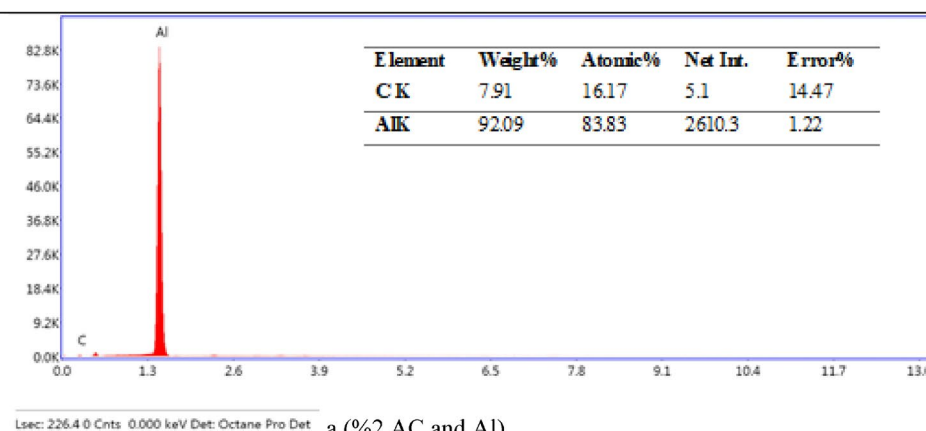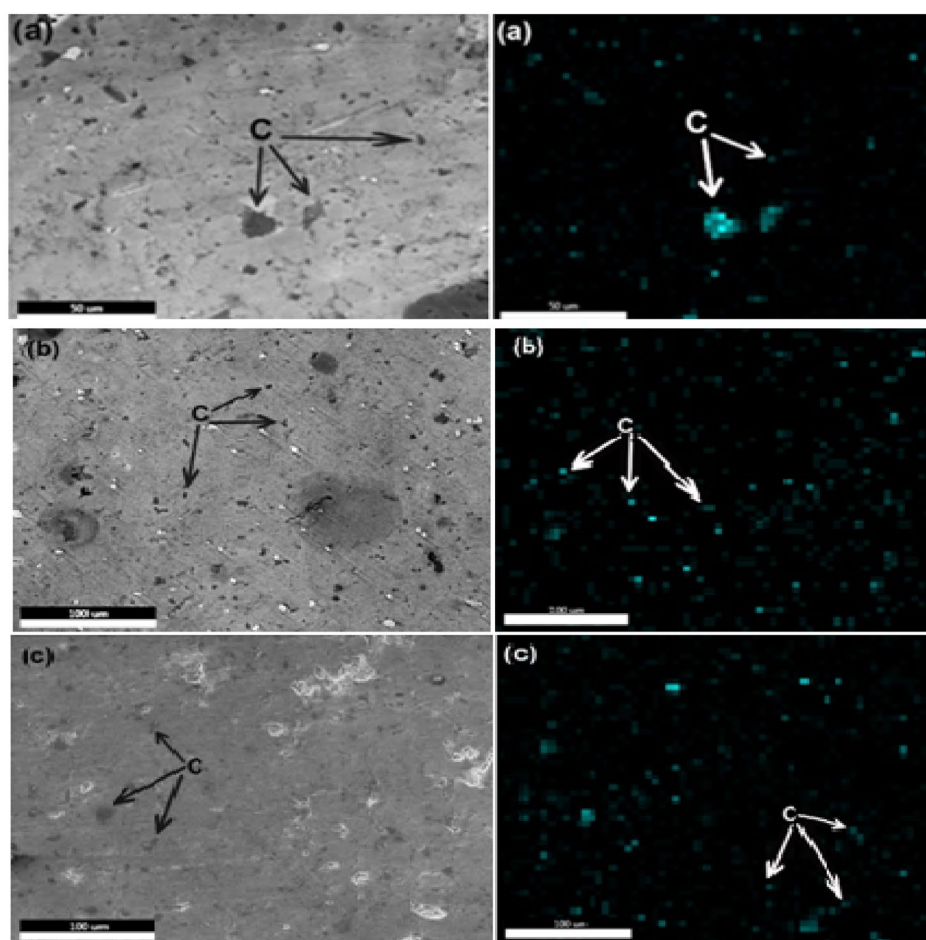


a (%2 AC and Al)

optical images of 2, 4 and 6% by weight of added activated carbon, it was observed that the added activated carbon were homogeneously dispersed in Al, and the hardness of the composite material decreased with the added amount of activated carbon, and didn't undergo any agglomeration. At the same time, it is observed in the optical images that

an interface layer is formed between the Al/AC in the composite. The homogenous distribution of activated carbon positively contributes to the materials' mechanical properties. Heterogeneous distribution found in the added materials adversely affects the composite material hardness. It is

Fig. 1 (continued)

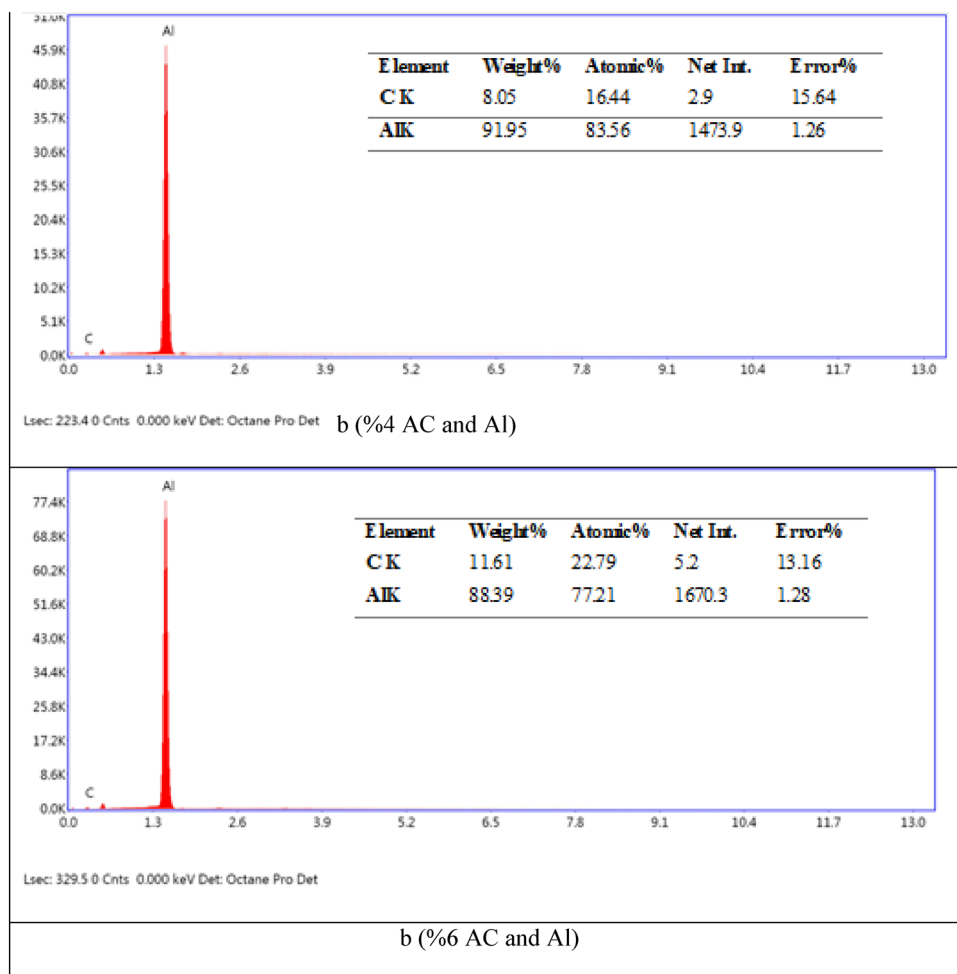

seen in the optical images that the added activated carbons are firmly held by the matrix.

The XRD results for aluminum, aluminum oxide and activated carbon are shown in Fig. 3. When the graphs were analyzed, peak intensity increased in parallel with the activated carbon quantity, which is added to Al. C peaks are observed in 6% activated carbon samples, although they are small. Again, when the graph is examined, the source of the Al_2O_3 peak is seen in the samples, which slightly oxidizes the surface during the preparation of the samples. This result also supports the EDS data.


Figure 4. shows that Vickers hardness test and this test was performed to monitor the effect of 2% to 6% mass of activated carbons on the matrix of aluminum alloy. The variation in hardness values of Al matrix composites is shown in Fig. 4. Pure aluminum has been observed to have less hardness. With the addition of 2% activated carbon, the hardness of the composites reached the highest value. The high stiffness of the composite materials was associated with the presence of hard particles of additive materials, which constitutes an obstacle to dislocation. Since the activated carbons are harder than aluminum, the amount

of activated carbon increase by mass decreases structural hardness.

Figure 5. shows the hardness change with increase in weight percentage of activated carbon. It is obvious in the figure that the lowest hardness existed in the case of pure aluminum; however, when activated carbon was increased to 2%, its microhardness value became the highest. The observed increase in hardness value was tripled as compared to pure aluminum. It also matched the previous Vickers hardness test results. Hardness decreased when activated carbon quantity was increased. This increases the activated carbon quantity, and weakens the matrix structure due to weak van der Waals interaction with aluminum, which reduces hardness; therefore, the best ratio of the activated carbon reinforcement to the aluminum matrix was found to be 2% activated carbon reinforcement. According to the elastic modulus graph shown in Fig. 6, the elastic modulus values increased by 3.4 times (9.59 GPa) compared to aluminum with the addition of 2% activated carbon. The elastic recovery rate was also quite low in Table 2.

Experimental and relative densities of Al matrix activated carbon with added composites are given in Table 2.

Fig. 2 Optical images of composites: A: %2AC + Al, B: %4AC + Al, C: %6AC + Al

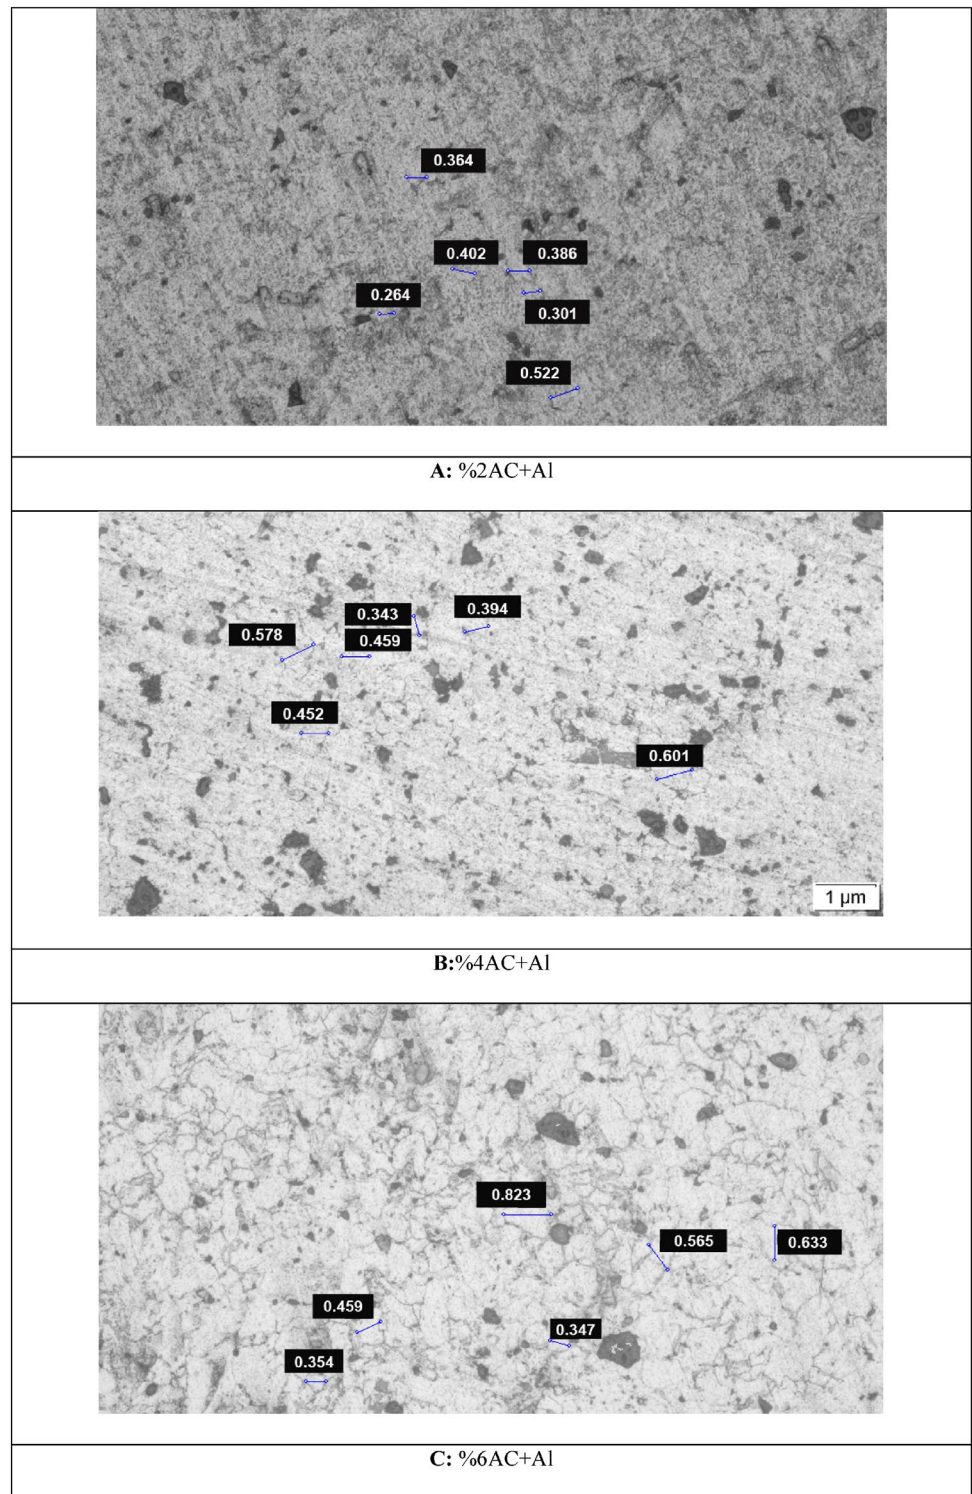

Experimental densities vary between 2.28 and 2.44 g/cm³ and theoretical densities vary between 2.54 and 2.70 g/cm³. As the amount of activated carbon added to the pure aluminum increases, the theoretical densities decrease compared to the experimental densities. This decrease in

density happens due to formation of pores in the Al matrix during sintering at 550 °C and the absorption of air into the pores. The relative densities vary between 88.80 and 95.6. High strength/density ratio is preferred in several engineering products.

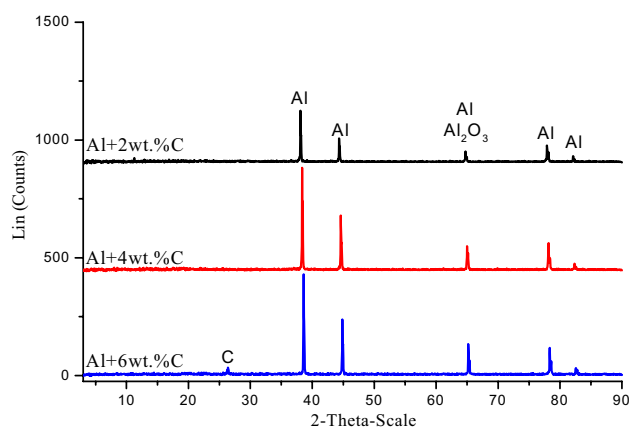


Fig. 3 XRD patterns of activated carbon and composites

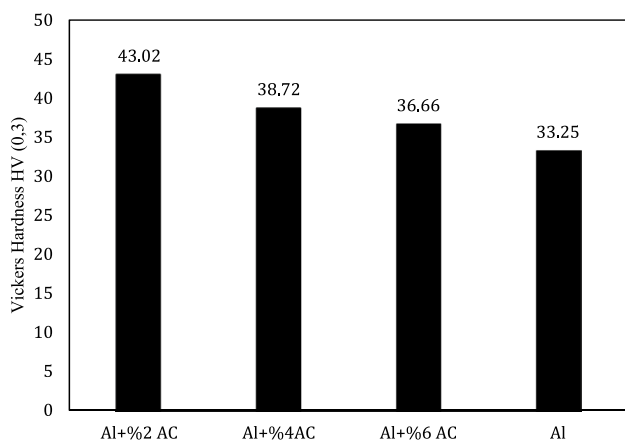


Fig. 4 Hardness values obtained by adding different activated carbon quantities to pure Al

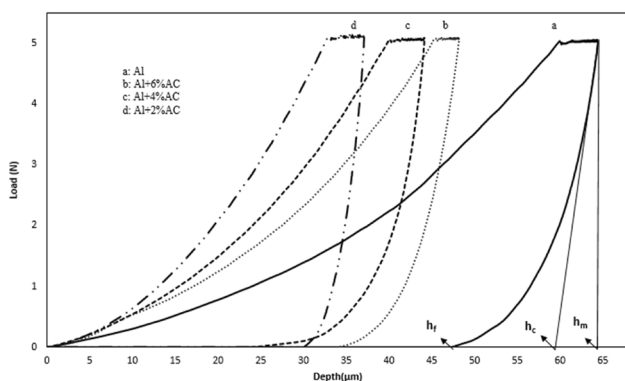


Fig. 5 Graph of loading–unloading/depth of activated carbons added to pure Al and Al in different

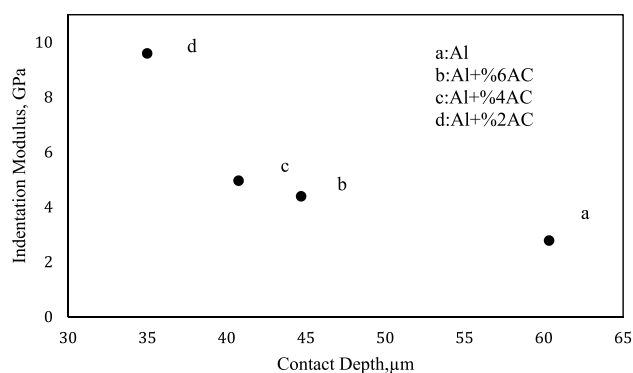


Fig. 6 Elastic modulus values obtained from dynamic hardness test

Table 2 Experimental and relative densities of Al / Activated carbon composites

Sample	Experimental density (gr/cm ³)	Theoretical density (gr/cm ³)	Relative density (%)
%2AC + Al	2.44	2.65	92.21
%4AC + Al	2.30	2.59	88.80
%6AC + Al	2.28	2.54	89.69
Raw Al	2.43	2.70	90.00

5 Conclusion

The composite material was obtained very successfully by using the activated carbon aluminum matrix powder metallurgical method obtained from the plant material. The activated carbons added according to SEM–EDS images are homogeneously dispersed in the aluminum matrix. According to optical photographs of the Al–AC composite material, as the amount of activated carbon added to the aluminum matrix increases, the average aluminum grain size decreases. In the XRD results, very little Al_2O_3 was formed, mainly due to the aluminum phase, which occurs due to oxidation. This phase also occurred during the production of the composite.

This increases the activated carbon quantity, and weakens the matrix structure due to weak van der Waals interaction with aluminum, which reduces hardness; therefore, the best ratio of the activated carbon reinforcement to the aluminum matrix was found to be 2% activated carbon reinforcement.

Vickers Hardness and Dynamic Micro Hardness results support each other too and the sample with 2% AC added has the highest hardness value. With the addition of 2% activated carbon, elastic modulus values increased by 3.4 times (9.59 GPa) compared to aluminum. Also as seen in Table 3, the elastic recovery rate is also quite low compared to the others.

Table 3 Changes of elastic recovery dynamic stiffness and elastic modulus of composite material with addition of activated carbon

Samples	Elastic recovery Rate($h_{\max}^{-1}$) (μm)	dynamic stiffness (GPa)	Elastic modulus (GPa)
Al	17.5	0.056	2.77
Al + %2 AC	7	0.16	9.59
Al + %4 AC	14	0.12	4.95
Al + %6AC	13.3	0.10	4.40

Acknowledgements This manuscript was taking from master thesis of Ayman M. S. EISAY. Thank you for his thesis process in Kastamonu university.

Funding This research did not receive any specific grant from funding agencies in the public, commercial, or not-for-profit sectors.

Declaration

Conflicts of interest The authors have no conflicts of interest to declare that are relevant to the content of this article.

References

- M.F. Kılıçaslan, E. Karakose, Production of CNT- bearing melt-spun Al-2Sc-0.05CNT alloys. *J. Alloy. Compd.* **738**, 182–187 (2018)
- M. Dev Anand, K.A. Janardhanan, P. Gopu, I.J. Rohit, Processing and characterization of aluminium based activated carbon composite made by enhanced stir die casting method. *J. Chem. Pharm. Sci.* **9**(1), 356–359 (2016)
- T.V. Christy, N. Murugan, S. Kumar, “A Comparative Study on the Microstructures and Mechanical Properties of Al 6061 Alloy and the MMC Al. *J. Miner. Mater. Charact. Eng.* **9**(1), 57–65 (2010)
- S. Islak, Mechanical and Corrosion Properties of AlCu Matrix Hybrid Composite Materials. *Sci. Sinter.* **51**, 81–92 (2019)
- M. Sayuti, S. Sulaiman, B. T. H. T. Baharudin, and M. K. A. Arifin, “Metal Matrix Composite Products by Vibration Casting Method,” *Ref. Modul. Mater. Sci. Mater. Eng.*, (2015).
- N. Michailidis, F. Stergioudi, A. Tsouknidas, Deformation and energy absorption properties of powder-metallurgy produced Al foams. *Mater. Sci. Eng. A* **528**(24), 7222–7227 (2011)
- A. Bafekry, C. Stampfl, Band-gap control of graphenelike boron-carbonitride g- BC 6 N bilayers by electrical gating. *Phys. Rev. B* **102**(19), 195411 (2020)
- A. Bafekry, A. Sarsari, I., M. Faraji, M. Fadlallah, M., H. R. Jap-por, S. Karbasizadeh, ... & Ghergherehchi, M., , Electronic and magnetic properties of two-dimensional of FeX (X= S, Se, Te) monolayers crystallize in the orthorhombic structures. *Appl. Phys. Lett.* **118**(14), 143102 (2021)
- A. Bafekry, M. Faraji, D.M. Hoat, M. Shahrokhi, M.M. Fadlallah, F. Shojaei, D. Gogova, MoSi₂N₄ single-layer: a novel two-dimensional material with outstanding mechanical, thermal, electronic and optical properties. *J. Phys. D: Appl. Phys.* **54**(15), 155303 (2021)
- A. Bafekry, M.M. Obeid, C.V. Nguyen, M. Ghergherehchi, M.B. Tagani, Graphene hetero-multilayer on layered platinum mineral jacutingaite (Pt₂ HgSe₃): van der Waals heterostructures with novel optoelectronic and thermoelectric performances. *J. Mater. Chem. A* **8**(26), 13248–13260 (2020)
- A. Baradeswaran, A.E. Perumal, Wear and mechanical characteristics of Al 7075/graphite composites. *Compos. Part B Eng.* **56**(August), 472–476 (2014)
- Y. Huang, Q. Ouyang, D. Zhang, J. Zhu, R. Li, H. Yu, Carbon materials reinforced aluminum composites: A review. *Acta Metall. Sin. English Lett.* **27**(5), 775–786 (2014)
- K.M. Shorowordi, T. Laoui, A.S.M.A. Haseeb, J.P. Celis, L. Froyen, Microstructure and interface characteristics of B4C, SiC and Al₂O₃ reinforced Al matrix composites: A comparative study. *J. Mater. Process. Technol.* **142**(3), 738–743 (2003)
- U. Balasubramani, R. Venkatesh, S. Subramaniam, G. Gopalakrishnan, V. Sundararajan, Alumina/activated carbon nanocomposites: Synthesis and application in sulphide ion removal from water. *J. Hazard. Mater.* **340**(July), 241–252 (2017)
- Y. Zamri and J. B. Shamsul, “Physical properties and wear behaviour of aluminium matrix composite reinforced with palm shell activated carbon (PSAC),” *Met. Mater.*, (2011).
- A. Türkyilmaz, M. Doğan, M. Alkan, characterization and adsorption properties of activated carbon prepared from olive stones. *Fresenius Environ. Bull.* **23**, 7a (2014)
- D. K. Ludlow, “Activated Carbon Adsorption By Roop Chand Bansal and Meenakshi Goyal (Panjab University, Chandigarh, India). CRC Press (an imprint of Taylor and Francis Group): Boca Raton, FL. 2005. xxii + 498 pp. \$189.95. ISBN 0–8247–5344–5.,” *J. Am. Chem. Soc.*, (2006).
- I. Noijuntira and P. Kittisupakorn, “Life Cycle Assessment for the Activated Carbon Production by Coconut Shells and Palm-Oil Shells,” 2nd RMUTP Int. Conf. (2010).
- H.Y. Seo, L.R. Jiang, C.G. Kang, C.K. Jin, Effect of compression process of MWCNT-reinforced Al6061 powder on densification characteristics and its mechanical properties. *Metals (Basel)* **7**(10), 437 (2017)
- R. Deaquino-Lara, N. Soltani, A. Bahrami, E. Gutierrez-Castaneda, E. Garcia-Sanchez, M.A.L. Hernandez-Rodriguez, Tribological characterization of Al7075- graphite composites fabricated by mechanical alloying and hot extrusion. *Mater. Des.* **67**, 224–231 (2015)

Publisher's Note Springer Nature remains neutral with regard to jurisdictional claims in published maps and institutional affiliations.